

# Effect of hyaluronic acid on morphological changes to dentin surfaces and subsequent effect on periodontal ligament cell survival, attachment, and spreading

Andrea Mueller<sup>1</sup> · Masako Fujioka-Kobayashi<sup>2,3</sup> · Heinz-Dieter Mueller<sup>4</sup> · Adrian Lussi<sup>4</sup> · Anton Sculean<sup>5</sup> · Patrick R. Schmidlin<sup>1,4</sup> · Richard J. Miron<sup>4,5,6</sup>

Received: 11 January 2016 / Accepted: 11 May 2016  
© Springer-Verlag Berlin Heidelberg 2016

## Abstract

**Objectives** Hyaluronic acid (HA) is a natural constituent of connective tissues and plays an important role in their development, maintenance, and regeneration. Recently, HA has been shown to improve wound healing. However, no basic in vitro study to date has investigated its mode of action. Therefore, the purpose of this study was to examine morphological changes of dentin surfaces following HA coating and thereafter investigate the influence of periodontal ligament (PDL) cell survival, attachment, and spreading to dentin discs. **Materials and methods** HA was coated onto dentin discs utilizing either non-cross-linked (HA) or cross-linked (HA cl) delivery systems. Morphological changes to dentin discs were then assessed using scanning electron microscopy (SEM). Thereafter, human PDL cells were seeded under three in vitro conditions including (1) dilution of HA (1:100), (2) dilution of HA (1:10), and (3) HA coated directly to dentin discs. Samples were then investigated for PDL cell survival,

attachment, and spreading using a live/dead assay, cell adhesion assay, and SEM imaging, respectively.

**Results** While control dentin discs demonstrated smooth surfaces both at low and high magnification, the coating of HA altered surface texture of dentin discs by increasing surface roughness. HA cl further revealed greater surface texture/roughness likely due to the cross-linking carrier system. Thereafter, PDL cells were seeded on control and HA coated dentin discs and demonstrated a near 100 % survival rate for all samples demonstrating high biocompatibility of HA at dilutions of both 1:100 and 1:10. Interestingly, non-cross-linked HA significantly increased cell numbers at 8 h, whereas cross-linked HA improved cell spreading as qualitatively assessed by SEM. **Conclusions** The results from the present study demonstrate that both carrier systems for HA were extremely biocompatible and demonstrated either improved cell numbers or cell spreading onto dentin discs. Future in vitro and animal research is necessary to further characterize the optimal delivery system of HA for improved clinical use.

**Clinical relevance** HA is a highly biocompatible material that may improve PDL cell attachment or spreading on dentin.

✉ Richard J. Miron  
rmiron@nova.edu

<sup>1</sup> Clinic of Preventive Dentistry, Periodontology and Cariology, Center of Dental Medicine, University of Zurich, Zurich, Switzerland

<sup>2</sup> Department of Cranio-Maxillofacial Surgery, Bern University Hospital, Inselspital, Bern, Switzerland

<sup>3</sup> Department of Oral Surgery, Institute of Biomedical Sciences, Tokushima University Graduate School, Tokushima, Japan

<sup>4</sup> Department of Preventive, Restorative and Pediatric Dentistry, School of Dental Medicine, University of Bern, Bern, Switzerland

<sup>5</sup> Department of Periodontology, School of Dental Medicine, University of Bern, Bern, Switzerland

<sup>6</sup> Department of Periodontology, College of Dental Medicine, Nova Southeastern University, Fort Lauderdale, FL, USA

**Keywords** Hyaluronan · Growth factors · Periodontal regeneration · Soft tissue regeneration · Connective tissue regeneration · Wound healing

## Introduction

Chemotherapeutic agents are used in combination with mechanical standard treatment modalities involving nonsurgical [1] and surgical methods [2, 3] in the therapy of periodontitis. These antimicrobial reagents topically administered into the periodontal pocket aim to reduce the bacterial load [4, 5]. Their application is considered to support healing processes

mainly by reducing inflammatory parameters, e.g., bleeding on probing (BOP) and probing depth (PD) [6]. More, recently, a variety of growth factors such as platelet-derived growth factor and enamel matrix derivatives have gained interest for clinical applications as bioactive substances in regenerative procedures in periodontology [7].

Hyaluronic acid (HA)—also known as hyaluronan—was originally discovered in 1934 in the vitreous body of the eye and synthesized in 1964 [8]. It is a hydrophilic, negatively charged, nonsulfated polymer (up to  $10^5/10^7$  kDa) classified as a glycosaminoglycan [8]. This macromolecule forms a viscous gel-like structure and can be found localized in high concentrations in the extracellular matrix (ECM) of the skin, cartilage, and bone, and more recently has been identified in the periodontal ligament [9]. In contrast to other glycosaminoglycans, HA is synthesized on the cell surface of fibroblasts, chondroblasts, and osteoblasts thereby interacting with plasmamembrane-bound receptor CD44, which is subsequently released into the ECM and degraded by the activated hyaluronidase enzymatic complex [10]. HA is characterized by well-conserved structural properties and linked to several ECM proteins and collagenous fibers [11, 12] responsible for mediating cell adhesion, motility, migration, and proliferation [11, 12]. A variety of biological functions in wound-healing processes including angiogenesis and reepithelialization have been documented both in vitro and in vivo following topical application of HA [13, 14]. Furthermore, HA has played a prominent role as a treatment agent for chronic osteoarthritis and is frequently used in aesthetic surgery, dermatology, and ophthalmology, as well as for tissue engineering applications [8, 15].

In addition, the anti-inflammatory effect of HA applied as an adjunct to the conventional periodontitis therapy scheme in dentistry has been discussed [16]. In vitro studies have demonstrated that HA-induced reduction of periodontal pathogens including *Actinobacillus actinomycetemcomitans* (AAC) and *Porphyromonas gingivalis* (P.g.) [17]. Moreover, HA has been linked with minimizing early bacterial recolonialization after and in combination with mechanical debridement [18, 19]. Therefore, a significant decline of PD (0.2–0.9 mm) and BOP (2.28–19.5 %) compared to control groups has been observed in clinical studies using HA at different concentrations and dosage forms [20]. Noteworthy, the application mode of HA and the appropriate carrier system are important parameters for periodontitis therapy [20]. Therefore, the aim of the present study was to examine the biocompatibility of HA administered on dentin and the consequent biological outcome on periodontal ligament (PDL) cells in vitro. Furthermore, HA was further investigated using two different carriers/formulations to determine the preferred composition/formulation of HA for future clinical use. We hypothesize that HA stimulates the adhesion, proliferation, and spreading of PDL cells seeded on dentin disks in a concentration-dependent manner.

## Materials and methods

### Dentin disc preparation, cell source, and reagents

One hundred eighty bovine roots of freshly extracted teeth were separated from their crowns, and the approximate area was first ground flat and polished using water-cooled silicon carbide paper (Stuers, Erkrat, Germany) up to P4000 grit to a diameter of 6.0 mm and a thickness of 1.5–1.6 mm to fit directly into 96 well in vitro culture plates. Dentin discs were prepared using a diamond-coated trephine under constant water-cooling. The discs were then stored in the dark in tap water at a temperature of 4 °C until experimental seeding.

HA was kindly provided by Regedent (Switzerland) utilizing two carrier systems including non-cross-linked native HA (Hyadent, BioScience GmbH, Germany, Switzerland) as well as a cross-linked HA (Hyadent BG, BioScience GmbH, Germany), cross-linked to butanediol diglycidyl ether (BDDE). Both HA carrier systems were cultured at dilutions of 1:10 and 1:100 as well as by pre-coating discs slices with 10 µl of HA.

Primary human PDL cells were obtained from the middle third portion of three teeth extracted from healthy patients with no signs of periodontal disease extracted for orthodontic reasons as previously described [21, 22]. Following ethical approval by the university, written informed consent was obtained from all patients. Primary human PDL cells were detached from the tissue culture plastic using trypsin solution. Cells used for experimental seeding were from passages 4–6. Cells were cultured in a humidified atmosphere at 37 °C in growth medium consisting of DMEM (Gibco, Life technologies, Carlsbad, CA), 10 % fetal bovine serum (FBS; Gibco), and 1 % antibiotics (Gibco). For in vitro experiments, cells were seeded with HA in 96-well culture plates at a density of 5000 cells per well for all experiments including cell attachment, cell survival (live/dead assay), and morphological variation as qualitatively assessed via SEM.

### Scanning electron microscopy

Dentin discs were fixed in 1 % glutaraldehyde and 1 % formaldehyde for 2 days for scanning electron microscopy (SEM). Following serial dehydration with ethanol, samples were critical point dried (Type M.9202 Critical Point Dryer, Roth & Co. Hatfield, PA, USA) and allowed to dry overnight as previously described [23, 24]. The following day, samples were sputter coated using a Balzers Union Sputtering Device (DCM-010, Balzers, Liechtenstein) with 10 nm of gold and analyzed microscopically using a Philips XL30 FEG scanning electron microscope to determine surface variations between samples. Furthermore, primary human PDL cells seeded onto dentin discs with/without HA were also investigated for cell

surface spreading in response to the various HA coating and dilution protocols.

### Cell viability

Primary human PDL cells were seeded in 96-well plates at a density of 5000 cells per well onto dentin slices either coated with non-cross-linked HA (HA) at a dilution of 1:100, 1:10, or pre-coated HA, as well as cross-linked HA (HA cl) at a dilution of 1:100, 1:10 or pre-coated with HA cl. At 8 h post-cell seeding, cells were evaluated using a live-dead staining assay according to the manufacturer's protocol (Enzo Life Sciences AG; Lausen, Switzerland) as previously described [25]. Fluorescent images were captured with a fluorescent microscope (OLYMPUS BX51, Tokyo, Japan). Thereafter, cell viability was expressed as percentages of live versus dead cells following cell culture growth. In total, 15 images (5 images per sample in triplicate) were quantified for live versus dead cells using ImageJ software (Baltimore, Maryland, USA).

### Adhesion assay

Primary human PDL cells were seeded in 96-well plates at a density of 5000 cells per well onto dentin slices either coated on control, non-cross-linked HA at a dilution of 1:100, 1:10, or pre-coated HA as well as cross-linked HA at a dilution of 1:100, 1:10, or pre-coated with HA cl. Cells were quantified using fluorescent imaging (from live/dead assay) at 8 h for cell numbers as previously described [26]. At desired time point of 8 h, cells were washed with phosphate-buffered solution (PBS), fixed with 4 % formaldehyde solution (Grogg-Chemie AG, Stettlen, Switzerland) for 5 min, and mounted with VECTASHILD (Vector, Burlingame, CA). Fluorescent images were quantified with a fluorescent microscope (OLYMPUS BX51, Tokyo, Japan). Experiments were performed in triplicate with five images captured per group. Data were analyzed for statistical significance using one-way analysis of variance with Tukey's test ( $*p$  values  $<0.05$  was considered significant).


## Results

### Surface characteristics of dentin slices with/out HA coating

SEM was first utilized to visualize morphological variation in surface topography prior to HA coating (Figs. 1 and 2). Control dentin discs were characterized by the presence of very smooth surfaces at low magnification ( $\times 100$ ). Higher resolution SEM images demonstrated surfaces that were still smooth, but with slight variations in surface topography likely due to a smear layer present on dentin discs during preparation (Fig. 1). Following non-cross-linked HA coating, surface characteristics of dentin slices demonstrated a more roughened surface with the presence of a surface layer of HA found on their surfaces (Fig. 2b). Interestingly, analysis at the same magnification revealed that cross-linked HA (HA cl) demonstrated surfaces with more roughened surface topography with the presence of an observable cross-linked pattern found coated on dentin surfaces (Fig. 2c).


### PDL cell survival, attachment, and spreading

Morphological differences in HA coating were then investigated for effects on cell survival, attachment, and spreading of PDL cells (Figs. 3, 4, and 5). It was first observed that cells seeded on dentin discs demonstrated close to a 100 % survival rate irrespective of HA coating (Fig. 3). Therefore, the present in vitro conditions indicated that HA was an extremely biocompatible material that supported cell survival at either 1:10, 1:100, or surface coated dentin discs with HA with no significant differences in cell viability observed between groups (Fig. 3). Thereafter, cell numbers were quantified after 8 h to determine the effects of HA coating on cell attachment (Fig. 4). It was found that non-cross-linked HA showed significantly higher levels of PDL cells on both HA 1:10 and HA pre-coated surfaces when compared to control and HA 1:100 dentin discs (Fig. 4). The effects of cross-linked HA did not seem to significantly affect cell numbers (Fig. 4). Thereafter, cell spreading was qualitatively assessed using SEM imaging

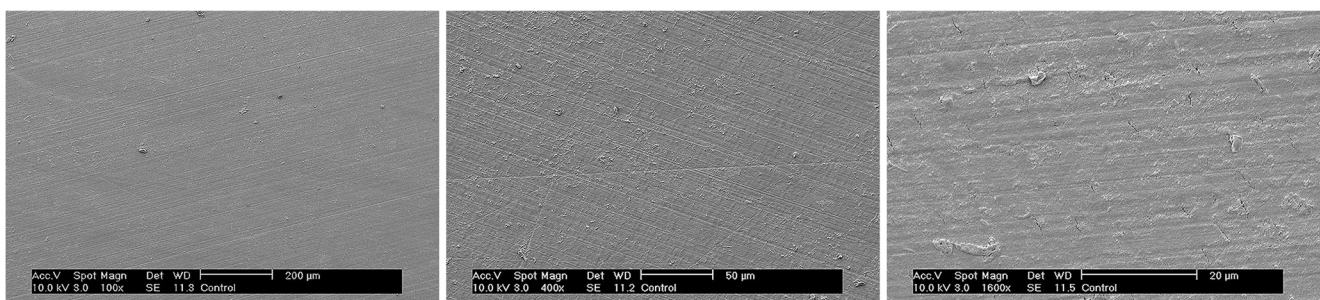

**Fig. 1** SEM images of control dentin slices at low ( $\times 100$ ), medium ( $\times 400$ ), and high ( $\times 1600$ ) magnification. Smooth surfaces were observed at low magnifications with slight variations observed at high magnification ( $\times 1600$ )



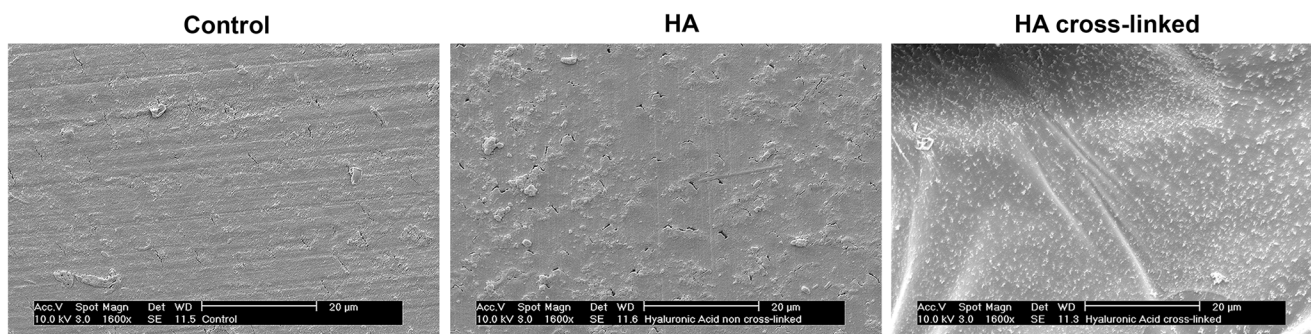

**Fig. 2** SEM images of control, non-cross-linked (HA) surfaces, and HA cross-linked surfaces at  $\times 1600$  magnification. Control surfaces demonstrated smooth surfaces, whereas surface roughness increased on non-cross-linked HA surfaces and cross-linked HA surfaces



(Fig. 5). It was found that cross-linked HA surfaces (HA cl) demonstrated more elongated cell shapes with more spreading observed on dentin discs when compared to control and regular HA surfaces (Fig. 5).


### Discussion

Successful periodontal regeneration following adequate infection control implies migration, adhesion, and proliferation of

periodontal progenitor and mesenchymal stem cells located in the intact part of the periodontal ligament toward the previously diseased root surface thus leading to formation of new cementum with inserting collagen fibers and of new alveolar bone [27–29]. In this context, the generation of synthetic and/or xenogenic scaffold systems combined with bioactive substances capable of supporting periodontal regenerative procedures is of major clinical interest. The focus of the present study was to evaluate the biological effect of native HA and cross-linked HA (HA cl) coated on dentin surfaces and to

**Fig. 3** Live/dead staining of primary human primary PDL cells on control, HA, and cross-linked HA surfaces. For cell viability, live-dead staining was done with viable cell appearing in *green* and dead cells in *red*. The results from these experiments demonstrated that HA is highly biocompatible at dilutions of 1:100 and 1:10 as well as pre-coated on dentin slices either utilizing regular or cross-linked HA carrier systems

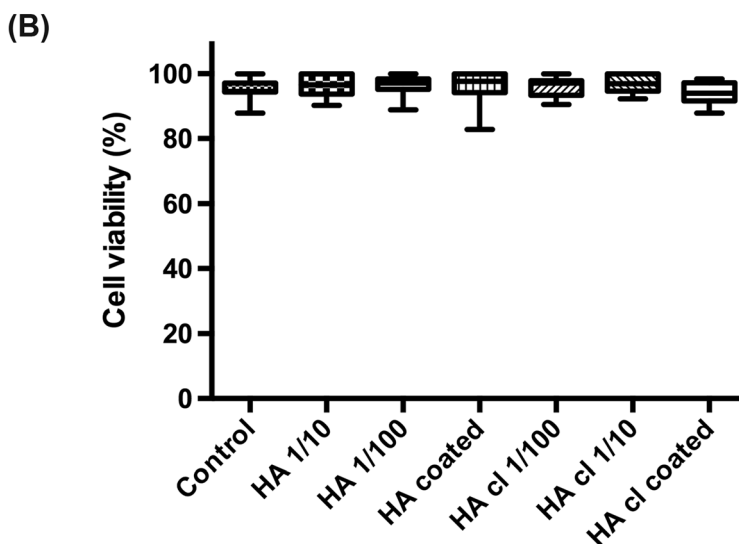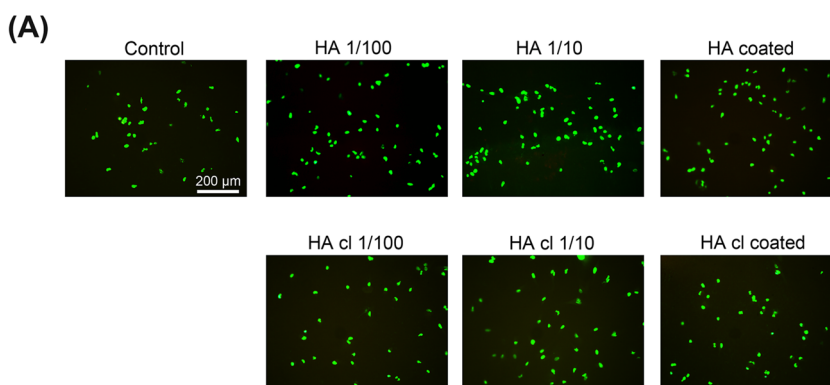

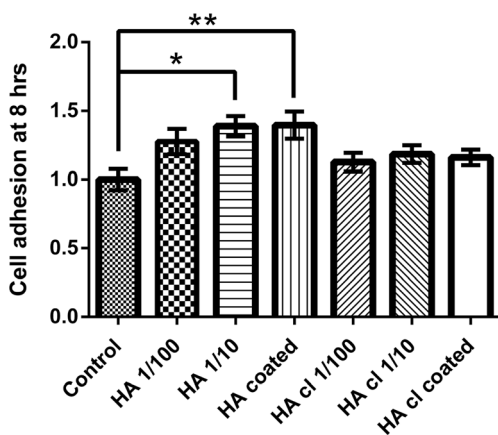


**Fig. 4** Cell number of primary human PDL cells seeded on control dentin slices and HA and HA cl dentin slices at dilutions 1:100, 1:10, and coated. Asterisk denotes significant difference when compared to control samples;  $p < 0.05$

study the viability, adhesion, and spreading of PDL cells upon HA treatment. We demonstrated (i) changes to the dentin surface topography following application of either HA or HA cl (Figs. 1 and 2), (ii) congruent biocompatibility of both carrier systems on the survival rate of PDL cells seeded on dentin discs (Fig. 3), and (iii) attachment of PDL cells compared to native HA and HA cl (Figs. 4 and 5) in a concentration-dependent manner as well as an increased PDL cell spreading on HA cl in contrast to non-cross-linked HA and control uncoated dentin surfaces.

Structured surfaces either naturally occurring on the tooth root or artificially developed in carrier systems [30] are necessary for cell adherence and spreading thereby forming elongated cell shapes [31]. Dangaria et al. (2011) showed a direct influence of root surface topography triggering PDL cell elongation thereby influencing periodontal fiber reattachment [32]. Here, the application of HA modified the dentin surfaces resulting in more roughness in both HA and HA cl when compared to noncoated control dentin surfaces (Figs. 1 and 2). In the presence of HA cl, the surface developed an even more

distinctive surface roughness with cross-linked fibrils found more evenly distributed throughout the dentin surfaces. The observed effect of either high molecular mass HA (HMW ~4000 kDa) and HA cl may be due to their physiochemical properties. HMW HA has previously been characterized by an optimal viscoelasticity, prolonged dwell time, and extended biocompatibility [33]. Previous studies performed in pulps treated with HMW HA resulted in the production of calcification nodules inducing reparative dentin formation [34]. Therefore, accumulation of HMW HA and its hydration effect on the coated dentin surface structure exposing tubules upon chemical treatment could establish an ideal network for cells to settle. The formation of precipitates due to degradation of HMW HA into smaller fragments may evoke the upregulation of genes involved in the proliferation and migration of cells [35]. Based on these observations, we conclude that either HA or HA cl applied to dentin surfaces provide an optimal surface topography resulting in advanced cell attachment.

Biodegradation, mechanical stress resistance, and biocompatibility are required features of medical devices maintaining optimal deposition of bioactive molecules thereby accelerating healing processes. The favorable effect of HA on the viability of various cell types, e.g., odontoblasts and fibroblasts [36] and PDL cells in vitro [37] has been reported previously. Combination of HA cross-linked to BDDE [38, 39] commercially used in dermal fillers (e.g. Restylane), adhesion barriers, and drug delivery results in prolonged residence time and accumulation of HA products [40]. Cell viability and survival are not affected using BDDE [41]. Previous studies comparing HA and HA cl concerning biological decay reported more stress resistance of HA cl. Moreover, both pure HA solutions (0.3–10 %) and HA cl resulted in an anti-inflammatory response downregulating nitrous oxide production by macrophages in a concentration-dependent manner in the presence of BDDE (0.1–1.0 ppm) [40]. Here, we observed cells seeded on HA and HA cl dentin

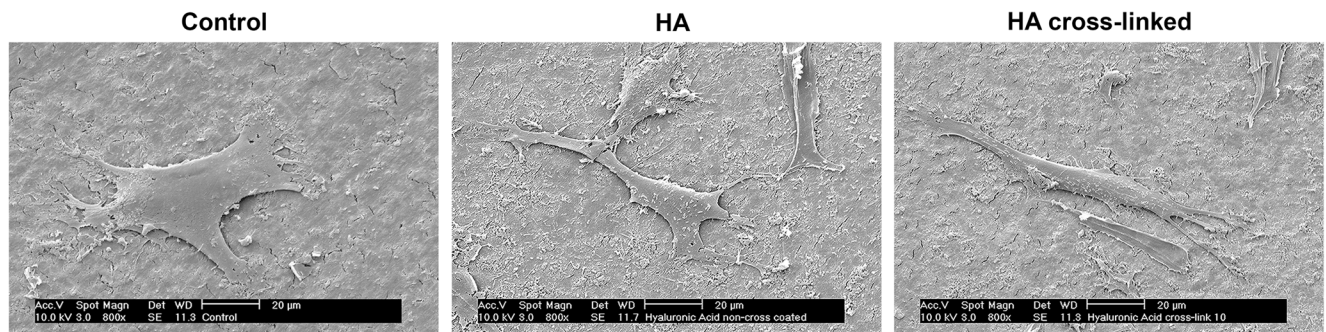

**Fig. 5** SEM images of primary human PDL cells seeded on control dentin, HA, and HA cl dentin slices. PDL cells seeded on cross-linked HA demonstrated qualitatively more elongated cell morphology when compared to control and HA surfaces

discs surviving up to 100 % at concentrations between 1:10 and 1:100 (Figs. 3 and 4). Moreover, Fujioka-Kobayashi et al. reported unaffected PDL cell viability under similar treatment conditions on plastic dish (unpublished data). Hence, both systems are considered exceptionally biocompatible with the ability to further stimulate PDL cell attachment and spreading in vitro.

The concentration-dependent exertion of externally added HA on cell behavior has been discussed controversially. Former investigators found induction of signal transduction and activation of intracellular cell cycle-related pathways depending on the cell type used upon HA treatment at high concentrations [42, 43]. The biological role of HA on cell migration and proliferation is yet not fully understood. David-Raoudi et al. reported increasing proliferation of fibroblasts in the presence of HA ranging in concentrations from 1 up to 5 mg/ml compared to HA oligosaccharide fragments [44]. In wound repair and early phases of inflammation, HMW HA has been shown to suppress collagen and protein synthesis in human skin fibroblasts [42]. Moreover, HMW HA inhibited the expression of cytokines, e.g., TNF- $\alpha$ , IL-1 $\beta$ , and IL-6 involved in inflammatory processes [45]. Further, HMW HA interaction with the ubiquitously transmembranous located CD44 adhesion receptor affects cell adhesion, proliferation, and HA metabolism [13]. We therefore speculate that HA and likely more so HA cl exert their biological function on PDL cells spreading due to the dentin surface topography and the interaction with membrane-located adhesion molecules. Taken together, our results confirm the exceptionally high biocompatibility of HA and HA cl on PDL cell survival. Moreover, HA was shown to significantly increase either cell adhesion or spreading onto dentin surfaces, both necessary events for the successful regeneration of periodontal tissues. Future animal as well as further in vitro studies are necessary to investigate the regeneration potential and cell-to-cell interaction level including their participating molecules.

**Acknowledgments** The authors thank Catherine Solioz for her careful technical assistance in helping with the experiments.

#### Compliance with ethical standards

**Conflict of interest** All authors declare that there are no conflicts of interest.

**Funding** This work was funded by Regedent who also supplied the HA carriers utilized in the present manuscript.

**Ethical approval** This article does not contain any studies with human participants or animals performed by any of the authors.

**Informed consent** For this type of study, formal consent is not required.

## References

1. Bollen CM, Quirynen M (1996) Microbiological response to mechanical treatment in combination with adjunctive therapy. A review of the literature. *J Periodontol* 67:1143–1158. doi:10.1902/jop.1996.67.11.1143
2. Heitz-Mayfield LJ, Lang NP (2013) Surgical and nonsurgical periodontal therapy. Learned and unlearned concepts. *Periodontol* 2000(62):218–231. doi:10.1111/prd.12008
3. Bonito AJ, Lux L, Lohr KN (2005) Impact of local adjuncts to scaling and root planing in periodontal disease therapy: a systematic review. *J Periodontol* 76:1227–1236. doi:10.1902/jop.2005.76.8.1227
4. Pilloni A, Annibali S, Dominici F, Di Paolo C, Papa M, Cassini MA, Polimeni A (2011) Evaluation of the efficacy of an hyaluronic acid-based biogel on periodontal clinical parameters. A randomized-controlled clinical pilot study. *Ann Stomatol* 2:3–9
5. Salvi GE, Mombelli A, Mayfield L, Rutar A, Suvan J, Garrett S, Lang NP (2002) Local antimicrobial therapy after initial periodontal treatment. *J Clin Periodontol* 29:540–550
6. Bonito AJ, Lohr KN, Lux L, Sutton S, Jackman A, Whitener L, Evensen C (2004) Effectiveness of antimicrobial adjuncts to scaling and root-planing therapy for periodontitis. *Evid Rep Technol Assess (Summ)* 88:1–4
7. Sukumar S, Drizhal I (2007) Hyaluronic acid and periodontitis. *Acta Medica (Hradec Kralove)* 50:225–228
8. Price RD, Berry MG, Navsaria HA (2007) Hyaluronic acid: the scientific and clinical evidence. *J Plast Reconstr Aesthet Surg* 60: 1110–1119. doi:10.1016/j.bjps.2007.03.005
9. Ohno S, Ijuin C, Doi T, Yoneno K, Tanne K (2002) Expression and activity of hyaluronidase in human periodontal ligament fibroblasts. *J Periodontol* 73:1331–1337. doi:10.1902/jop.2002.73.11.1331
10. Triggs-Raine B, Natowicz MR (2015) Biology of hyaluronan: insights from genetic disorders of hyaluronan metabolism. *World J Biol Chem* 6:110–120. doi:10.4331/wjbc.v6.i3.110
11. Oksala O, Salo T, Tammi R, Hakkinen L, Jalkanen M, Inki P, Larjava H (1995) Expression of proteoglycans and hyaluronan during wound healing. *J Histochem Cytochem* 43:125–135
12. Tajima S (1996) Fibrous-long spacing fiber formation by collagen and non-collagenous acidic components from calf skin. *J Dermatol Sci* 12:104–109
13. Chen WY, Abatangelo G (1999) Functions of hyaluronan in wound repair. *Wound Repair Regen* 7:79–89
14. Bevilacqua L, Eriani J, Serroni I, Liani G, Borelli V, Castronovo G, Di Lenarda R (2012) Effectiveness of adjunctive subgingival administration of amino acids and sodium hyaluronate gel on clinical and immunological parameters in the treatment of chronic periodontitis. *Ann Stomatol* 3:75–81
15. Neuman MG, Nanau RM, Oruna-Sanchez L, Coto G (2015) Hyaluronic acid and wound healing. *J Pharm Pharm Sci* 18:53–60
16. Engstrom PE, Shi XQ, Tronje G, Larsson A, Welander U, Frithiof L, Engstrom GN (2001) The effect of hyaluronan on bone and soft tissue and immune response in wound healing. *J Periodontol* 72: 1192–1200. doi:10.1902/jop.2000.72.9.1192
17. Pirnazar P, Wolinsky L, Nachnani S, Haake S, Pilloni A, Bernard GW (1999) Bacteriostatic effects of hyaluronic acid. *J Periodontol* 70:370–374. doi:10.1902/jop.1999.70.4.370
18. Johannsen A, Tellefsen M, Wikesjo U, Johannsen G (2009) Local delivery of hyaluronan as an adjunct to scaling and root planing in the treatment of chronic periodontitis. *J Periodontol* 80:1493–1497. doi:10.1902/jop.2009.090128
19. Eick S, Renatus A, Heinicke M, Pfister W, Stratul SI, Jentsch H (2013) Hyaluronic acid as an adjunct after scaling and root planing: a prospective randomized clinical trial. *J Periodontol* 84:941–949. doi:10.1902/jop.2012.120269



20. Bertl K, Bruckmann C, Isberg PE, Klinge B, Gotfredsen K, Stavropoulos A (2015) Hyaluronan in non-surgical and surgical periodontal therapy: a systematic review. *J Clin Periodontol* 42: 236–246. doi:10.1111/jcpe.12371
21. Miron RJ, Bosshardt DD, Hedbom E, Zhang Y, Haenni B, Buser D, Sculean A (2012) Adsorption of enamel matrix proteins to a bovine-derived bone grafting material and its regulation of cell adhesion, proliferation, and differentiation. *J Periodontol* 83:936–947. doi:10.1902/jop.2011.110480
22. Miron RJ, Caluseru OM, Guillemette V, Zhang Y, Gemperli AC, Chandad F, Sculean A (2013) Influence of enamel matrix derivative on cells at different maturation stages of differentiation. *PLoS One* 8:e71008. doi:10.1371/journal.pone.0071008
23. Miron RJ, Gruber R, Hedbom E, Saulacic N, Zhang Y, Sculean A, Bosshardt DD, Buser D (2013) Impact of bone harvesting techniques on cell viability and the release of growth factors of autografts. *Clin Implant Dent Relat Res* 15:481–489. doi:10.1111/j.1708-8208.2012.00440.x
24. Miron RJ, Hedbom E, Saulacic N, Zhang Y, Sculean A, Bosshardt DD, Buser D (2011) Osteogenic potential of autogenous bone grafts harvested with four different surgical techniques. *J Dent Res* 90: 1428–1433. doi:10.1177/0022034511422718
25. Sawada K, Caballe-Serrano J, Bosshardt DD, Schaller B, Miron RJ, Buser D, Gruber R (2015) Antiseptic solutions modulate the paracrine-like activity of bone chips: differential impact of chlorhexidine and sodium hypochlorite. *J Clin Periodontol*. doi:10.1111/jcpe.12447
26. Miron RJ, Oates CJ, Molenberg A, Dard M, Hamilton DW (2010) The effect of enamel matrix proteins on the spreading, proliferation and differentiation of osteoblasts cultured on titanium surfaces. *Biomaterials* 31:449–460. doi:10.1016/j.biomaterials.2009.09.075
27. Nyman S, Lindhe J, Karring T, Rylander H (1982) New attachment following surgical treatment of human periodontal disease. *J Clin Periodontol* 9:290–296
28. Melcher AH (1976) On the repair potential of periodontal tissues. *J Periodontol* 47:256–260. doi:10.1902/jop.1976.47.5.256
29. Melcher AH, Chan J (1981) Phagocytosis and digestion of collagen by gingival fibroblasts in vivo: a study of serial sections. *J Ultrastruct Res* 77:1–36
30. Fitton JH, Dalton BA, Beumer G, Johnson G, Griesser HJ, Steele JG (1998) Surface topography can interfere with epithelial tissue migration. *J Biomed Mater Res* 42:245–257
31. Dunn GA, Brown AF (1986) Alignment of fibroblasts on grooved surfaces described by a simple geometric transformation. *J Cell Sci* 83:313–340
32. Dangaria SJ, Ito Y, Luan X, Diekwisch TG (2011) Successful periodontal ligament regeneration by periodontal progenitor preseeded on natural tooth root surfaces. *Stem Cells Dev* 20:1659–1668. doi:10.1089/scd.2010.0431
33. Guidolin D, Franceschi F (2014) Viscosupplementation with high molecular weight native hyaluronan. Focus on a 1500–2000 kDa fraction (Hyalubrix(R)). *Eur Rev Med Pharmacol Sci* 18:3326–3338
34. Sasaki T, Kawamata-Kido H (1995) Providing an environment for reparative dentine induction in amputated rat molar pulp by high molecular-weight hyaluronic acid. *Arch Oral Biol* 40:209–219
35. Tsepilov RN, Beloded AV (2015) Hyaluronic acid - an “old” molecule with “new” functions: biosynthesis and depolymerization of hyaluronic acid in bacteria and vertebrate tissues including during carcinogenesis. *Biochem Biokhimiia* 80:1093–1108. doi:10.1134/s0006297915090011
36. Bogovic A, Nizetic J, Galic N, Zeljezic D, Micek V, Mladinic M (2011) The effects of hyaluronic acid, calcium hydroxide, and dentin adhesive on rat odontoblasts and fibroblasts. *Arh Hig Rada Toksikol* 62:155–161. doi:10.2478/10004-1254-62-2011-2076
37. Akizuki T, Oda S, Komaki M, Tsuchioka H, Kawakatsu N, Kikuchi A, Yamato M, Okano T, Ishikawa I (2005) Application of periodontal ligament cell sheet for periodontal regeneration: a pilot study in beagle dogs. *J Periodontol Res* 40:245–251. doi:10.1111/j.1600-0765.2005.00799.x
38. Choi S, Choi W, Kim S, Lee SY, Noh I, Kim CW (2014) Purification and biocompatibility of fermented hyaluronic acid for its applications to biomaterials. *Biomater Res* 18:6. doi:10.1186/2055-7124-18-6
39. Yeom J, Hwang BW, Yang DJ, Shin HI, Hahn SK (2014) Effect of osteoconductive hyaluronate hydrogels on calvarial bone regeneration. *Biomater Res* 18:8. doi:10.1186/2055-7124-18-8
40. Choi SC, Yoo MA, Lee SY, Lee HJ, Son DH, Jung J, Noh I, Kim CW (2015) Modulation of biomechanical properties of hyaluronic acid hydrogels by crosslinking agents. *J Biomed Mater Res A* 103: 3072–3080. doi:10.1002/jbm.a.35437
41. Nishi C, Nakajima N, Ikada Y (1995) In vitro evaluation of cytotoxicity of diepoxy compounds used for biomaterial modification. *J Biomed Mater Res* 29:829–834. doi:10.1002/jbm.820290707
42. Croce MA, Dyne K, Boraldi F, Quaglino D Jr, Cetta G, Tiozzo R, Pasquali Ronchetti I (2001) Hyaluronan affects protein and collagen synthesis by in vitro human skin fibroblasts. *Tissue Cell* 33: 326–331. doi:10.1054/tice.2001.0180
43. Moon SO, Lee JH, Kim TJ (1998) Changes in the expression of c-myc, RB and tyrosine-phosphorylated proteins during proliferation of NIH 3T3 cells induced by hyaluronic acid. *Exp Mol Med* 30:29–33. doi:10.1038/emmm.1998.4
44. David-Raoudi M, Tranchepain F, Deschrevel B, Vincent JC, Bogdanowicz P, Boumediene K, Pujol JP (2008) Differential effects of hyaluronan and its fragments on fibroblasts: relation to wound healing. *Wound Repair Regen* 16:274–287. doi:10.1111/j.1524-475X.2007.00342.x
45. Takeda K, Sakai N, Shiba H, Nagahara T, Fujita T, Kajiyama M, Iwata T, Matsuda S, Kawahara K, Kawaguchi H, Kurihara H (2011) Characteristics of high-molecular-weight hyaluronic acid as a brain-derived neurotrophic factor scaffold in periodontal tissue regeneration. *Tissue Eng A* 17:955–967. doi:10.1089/ten.TEA.2010.0070